



# 2D/2D Graphitic Carbon Nitride (g-C<sub>3</sub>N<sub>4</sub>) Heterojunction Nanocomposites for Photocatalysis: Why Does Face-to-Face Interface Matter?

Wee-Jun Ong\*

*Institute of Materials Research and Engineering (IMRE), Agency for Science, Technology and Research (A\*STAR), Innovis, Singapore, Singapore*

## OPEN ACCESS

### Edited by:

Wei Lv,  
Tsinghua University, China

### Reviewed by:

Chen Zhang,  
Tianjin University, China  
Yi Wen Phuan,  
Monash University Malaysia, Malaysia

### \*Correspondence:

Wee-Jun Ong  
ongwj@imre.a-star.edu.sg,  
ongweejun@gmail.com,  
<https://sites.google.com/site/wjongresearch/>

### Specialty section:

This article was submitted to  
Carbon-Based Materials,  
a section of the journal  
Frontiers in Materials

**Received:** 26 January 2017

**Accepted:** 17 March 2017

**Published:** 12 April 2017

### Citation:

Ong W-J (2017) 2D/2D Graphitic Carbon Nitride (g-C<sub>3</sub>N<sub>4</sub>) Heterojunction Nanocomposites for Photocatalysis: Why Does Face-to-Face Interface Matter? *Front. Mater.* 4:11. doi: 10.3389/fmats.2017.00011

In recent years, two-dimensional (2D) graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) has elicited interdisciplinary research fascination among the scientific communities due to its attractive properties such as appropriate band structures, visible-light absorption, and high chemical and thermal stability. At present, research aiming at engineering 2D g-C<sub>3</sub>N<sub>4</sub> photocatalysts at an atomic and molecular level in conquering the global energy demand and environmental pollution has been thriving. In this review, the cutting-edge research progress on the 2D/2D g-C<sub>3</sub>N<sub>4</sub>-based hybrid nanoarchitectures will be systematically highlighted with a specific emphasis on a multitude of photocatalytic applications, not only in waste degradation for pollution alleviation, but also in renewable energy production [e.g., water splitting and carbon dioxide (CO<sub>2</sub>) reduction]. By reviewing the substantial developments on this hot research platform, it is envisioned that the review will shed light and pave a new prospect for constructing high photocatalytic performance of 2D/2D g-C<sub>3</sub>N<sub>4</sub>-based system, which could also be extended to other related energy fields, namely solar cells, supercapacitors, and electrocatalysis.

**Keywords:** graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>), photocatalysis, energy conversion, environmental remediation, 2D/2D heterojunction, face-to-face interface

## INTRODUCTION

Photocatalysis is emerged as one of the Holy Grails of sustainable and green technologies for solar energy conversion, energy storage, and environmental remediation, which has been intensively examined over the past few decades worldwide to search for novel photocatalysts (Inoue et al., 1979; Linsebigler et al., 1995; Ma et al., 2014; Ong et al., 2014a, 2016b; He and Que, 2016; Li et al., 2016a; Wenderich and Mul, 2016; Zhang et al., 2016a; Eftekhari, 2017; Liu et al., 2017; Osterloh, 2017; Roger et al., 2017). By harvesting solar energy as the source of renewable energy, photocatalysis will make significant impacts in the areas of (1) light-driven water splitting to hydrogen (H<sub>2</sub>) and oxygen (O<sub>2</sub>) (Chen et al., 2010; Bai et al., 2016; Wei et al., 2016; Putri et al., 2017; Yubin et al., 2017), (2) conversion of carbon dioxide (CO<sub>2</sub>) to energy bearing fuels (Ong et al., 2013, 2014c; Tan et al., 2014, 2016, 2017; Gui et al., 2015; Guo et al., 2016a; Zhang et al., 2016c), (3) mineralization of waste and pollutants (Ong et al., 2014d,e; Fang et al., 2016; Liu et al., 2016c; Topcu et al., 2016; Zhao et al., 2016b), (4) selective

organic transformations (Liu et al., 2014; Zhao et al., 2016a), and (5) disinfection of bacteria (Keane et al., 2014; Bing et al., 2015) (Figure 1). Very recently, two-dimensional (2D) semiconductor photocatalysts have triggered a renaissance of interest in the field of energy, and environmental-related applications thank to the high ratio of surface-to-volume and unprecedented electronic and optical characteristics (Ong et al., 2014b; Bai et al., 2015; Liang et al., 2015d; Fang et al., 2016; Kalantar-zadeh et al., 2016; She et al., 2017; Xueting et al., 2017). Among a large array of photocatalysts, research targeting at graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) has been flourishing in recent years. Since the first exploratory study on the use of g-C<sub>3</sub>N<sub>4</sub> in photocatalytic H<sub>2</sub> evolution in 2009 (Wang et al., 2009), there has been an exponential increase in the scientific research on the subject of g-C<sub>3</sub>N<sub>4</sub>-based materials with more than 800 publications in 2016 based on Web of Science.

By and large, g-C<sub>3</sub>N<sub>4</sub> can be facily prepared by nitrogen-rich precursors, namely urea, thiourea, melamine, and dicyandiamide (Han et al., 2015; Guo et al., 2016b; Zhou et al., 2016; Tong et al., 2017). Therefore, the development of g-C<sub>3</sub>N<sub>4</sub>-based photocatalysts is anticipated to surmount the issues of increasing concerns on fossil fuel depletion and environmental threats due to combustion of exhaustible fossil fuels. The metal-free g-C<sub>3</sub>N<sub>4</sub> demonstrates distinctive attributes such as visible-light responsiveness with moderate band gap of *ca.* 2.7 eV, appealing band structures and electronic characteristic, its earth-abundant nature, non-toxicity, relative ease of synthesis, and excellent chemical stability (Lu et al., 2016; Ong et al., 2016b; Zhang et al., 2016b; Lee et al., 2017). Additionally, it has been proven that 2D semiconductor possessed improved mobility of charge carriers and reduced charge recombination as compared to the 0D and 1D nanomaterials (Meng et al., 2012; Ida and Ishihara, 2014). In spite of the fascinating properties possessed by 2D g-C<sub>3</sub>N<sub>4</sub>, pristine g-C<sub>3</sub>N<sub>4</sub> demonstrated several shortfalls such as

sluggish separation of electron-hole pairs, limited visible-light absorption beyond 460 nm, small specific surface area, and low electrical conductivity (Liang et al., 2015b; Hou et al., 2016; Shi et al., 2016; Zhang et al., 2016g; Li et al., 2017; Xia et al., 2017). To overcome these bottlenecks, modification of bare g-C<sub>3</sub>N<sub>4</sub> such as nanostructure design (Niu et al., 2012; Liang et al., 2015c; Zheng et al., 2015), intercalation with Li<sup>+</sup> and Cl<sup>-</sup> (Liang et al., 2015a), elemental doping (Hu et al., 2015; Huang et al., 2015; She et al., 2016), copolymerization (Fan et al., 2016; Rahman et al., 2016), coupling with metals or noble metals (Tonda et al., 2014; Ong et al., 2015b), incorporation with other semiconductors (Ong et al., 2016a; Putri et al., 2016a; Zhang et al., 2016g; Ye et al., 2017), hybridization with metal phosphides (Pan et al., 2017; Wen et al., 2017; Yi et al., 2017; Zhao et al., 2017a,b), and many more has been widely investigated to enhance the photocatalytic efficiency for practical benefits. To date, there are a number of excellent review articles highlighting on g-C<sub>3</sub>N<sub>4</sub>-based photocatalysts ranging from materials synthesis, functionalization, and hybridization to diversified applications (Cao et al., 2015; Dong and Cheng, 2015; Yin et al., 2015; Zhang et al., 2015a; Zhao et al., 2015; Liu et al., 2016a; Mamba and Mishra, 2016). This undoubtedly connotes the significance of this research field hitherto in the scientific community.


Recently, the incorporation of 2D g-C<sub>3</sub>N<sub>4</sub> photocatalyst with other 2D nanomaterials forming 2D/2D heterojunction hybrid nanocomposites has conceivably drawn increasing attention with practical importance (Hou et al., 2014; Xing et al., 2017). As a matter of fact, the layered heterojunction comprised dissimilar 2D nanomaterials is projected to give rise to positive impacts on charge transfer and separation as a result of built-in electric field at the atomically well-defined ultrathin interface (Hou et al., 2013b; Lu et al., 2016). Thus, the research on 2D/2D heterojunction with intimate face-to-face interface is of timely significance, which will elucidate us to deeply comprehend the photocatalytic reaction mechanism at the molecular level. Therefore, in this review, this leads to my immense interest to summarize the state-of-the-art research on 2D/2D g-C<sub>3</sub>N<sub>4</sub> heterojunction nanohybrids to throw light on the future research horizon of g-C<sub>3</sub>N<sub>4</sub> in artificial photosynthesis and environmental remediation.


## DEVELOPMENT OF 2D/2D g-C<sub>3</sub>N<sub>4</sub>-BASED HETEROJUNCTION

It is well documented that 2D/2D nanocomposites bestow greater electron-hole mobility across the heterojunction interface, which will in turn reduce the distance and time of charge transport to impede the electron-hole recombination rate (Hou et al., 2013a; Cheng et al., 2015; Ong et al., 2015c). This is attributed to the larger 2D/2D face-to-face contact area compared with line-to-face contact in 1D/2D heterojunction and point-to-face contact in 0D/2D heterojunction as depicted in Figure 2.

## Hybridization with 2D Transition Metal Chalcogenides

In recent years, the incorporation of 2D metal sulfides has underpinned enormous interests in photocatalysis (Liu et al., 2016b; Lu

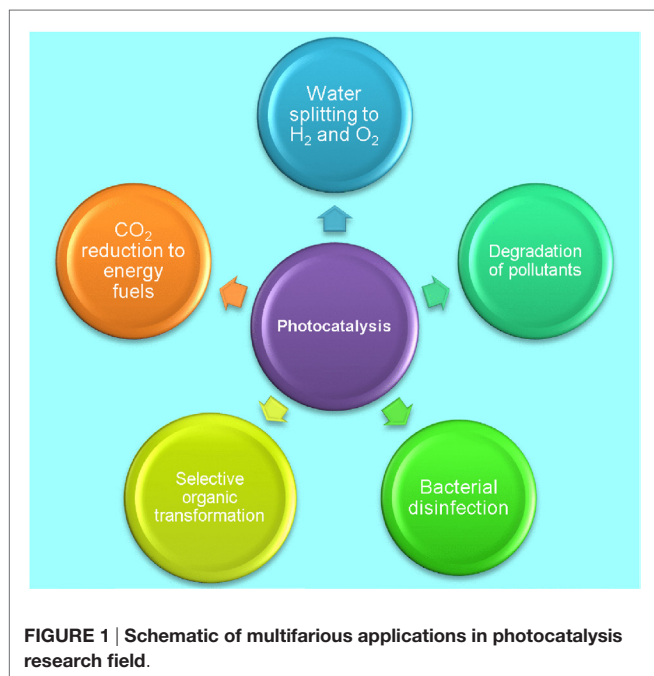

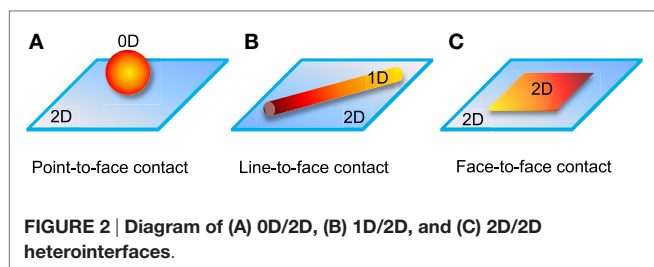

et al., 2016; Yu and Sivula, 2016). In a work by Dong's research group, they reported a hierarchical sheet-on-sheet ZnIn<sub>2</sub>S<sub>4</sub>/g-C<sub>3</sub>N<sub>4</sub> heterostructure by growing ultrathin ZnIn<sub>2</sub>S<sub>4</sub> onto g-C<sub>3</sub>N<sub>4</sub> nanosheets (Zhang et al., 2016e). As a result of intimate heterojunction interface formed between ZnIn<sub>2</sub>S<sub>4</sub> and g-C<sub>3</sub>N<sub>4</sub>, the hybrid nanocomposites demonstrated whopping 17.6- and 3.9-folds enhancement of H<sub>2</sub> evolution compared to the single component g-C<sub>3</sub>N<sub>4</sub> and ZnIn<sub>2</sub>S<sub>4</sub>, respectively. From the perspective of lifetime of charge carriers evidenced from time-resolved photoluminescence analysis, the average lifetime of the ZnIn<sub>2</sub>S<sub>4</sub>/g-C<sub>3</sub>N<sub>4</sub> nanohybrids was reduced from 10.45 to 8.97 ns relative to that of pristine g-C<sub>3</sub>N<sub>4</sub> nanosheets, which was attributed to rapid charge transfer and separation to hinder the electron-hole recombination. In addition to ZnIn<sub>2</sub>S<sub>4</sub>, MoS<sub>2</sub>-decorated S-doped g-C<sub>3</sub>N<sub>4</sub> heterojunction films were successfully developed by Chen and coworkers (Figure 3A) for enhanced photoelectrocatalysis (Ye et al., 2016). It is noted that the generation of anodic current by the MoS<sub>2</sub>/S-doped g-C<sub>3</sub>N<sub>4</sub> photoanode was markedly twice than that by the S-doped g-C<sub>3</sub>N<sub>4</sub>, highlighting the rational importance of a robust heterointerface with intact p-n junctions for effective charge migration (Figure 3B).

Till now, the theoretical understanding on the coupling interaction and transfer of charge carriers between 2D g-C<sub>3</sub>N<sub>4</sub> and 2D MoS<sub>2</sub> has not been exhaustively investigated. Wang et al. (2014) elucidated the fundamental mechanism of photocatalytic improvements by systematically exploring the interface region between MoS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub>. Based on the density functional theory (DFT) calculations, it was confirmed the presence of charge redistribution at the 2D/2D heterojunction interface of MoS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>. It is worth mentioning that a type II heterojunction structure was successfully developed due to the well-matched band alignment as attested by the density of states results. As a result of efficient migration of charge carriers, a polarized field was formed at the contact heterointerface, prohibiting the electron-hole recombination. Therefore, this DFT finding provides new inroads into the importance of constructing 2D/2D nanocomposites for face-to-face interaction, which could certainly be extended to other binary or even ternary layered heterojunction for enhanced photochemistry applications.

## Hybridization with 2D Metal Oxides


Apart from 2D transition metal chalcogenides, coupling g-C<sub>3</sub>N<sub>4</sub> nanosheets with 2D metal oxides, such as TiO<sub>2</sub> (Gu et al., 2014), WO<sub>3</sub> (Li et al., 2016b), and SnSb<sub>2</sub>O<sub>6</sub> (Zhang et al., 2016d), has become the recent research focus to improve the photocatalytic performance. For instance, Li et al. (2016b)

employed a hydrothermal and deposition-heating technique to fabricate WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> nanosheet arrays on the FTO substrates. The photoelectrochemical splitting of natural seawater using the WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> nanostructures presented two times greater in the photocurrent density in reference to the pristine WO<sub>3</sub> nanosheet arrays under the simulated sunlight source. This was accredited to the well-matched band energy of WO<sub>3</sub> and g-C<sub>3</sub>N<sub>4</sub> forming synergistic interfacial contacts for remarkably boosting the charge migration ability. In another work, Xing's group hybridized AgIO<sub>3</sub> with anisotropic g-C<sub>3</sub>N<sub>4</sub> nanosheets to form a 2D/2D layered heterointerface toward increased photodegradation of Rhodamine B and methyl orange pollutants (Li et al., 2015). It is anticipated that these works will lay a pioneer groundwork and shed light for future directions in the interface engineering of 2D metal oxides and g-C<sub>3</sub>N<sub>4</sub> for the advancement in solar energy conversion and environmental remediation toward practical applications.


Most recently, perovskite-type nitrogen-doped La<sub>2</sub>Ti<sub>2</sub>O<sub>7</sub> (NLTO), comprising a 2D architecture with a thickness of 7 nm, was for the first time hybridized with 2 nm thick g-C<sub>3</sub>N<sub>4</sub> nanosheets by means of a facile two-step hydrothermal method and a thermal treatment process (Figure 4A) (Cai et al., 2017). The hybrid layered nanomaterials showed excellent photocatalytic H<sub>2</sub> evolution with a high apparent quantum efficiency of 2.1% at 400 nm. The enhanced photoactivity was ascribed to the successful development of the large 2D/2D interface between NLTO and g-C<sub>3</sub>N<sub>4</sub>, resulting in long lifetime and favorable transfer of charge carriers *via* type II band alignment. Upon visible-light illumination, the photoexcited electrons were facilely migrated from g-C<sub>3</sub>N<sub>4</sub> to NLTO, whereas the photogenerated holes were transported from NLTO to g-C<sub>3</sub>N<sub>4</sub>, hampering the charge recombination process (Figure 4B). Notably, this was arisen from the band bending formed at the heterointerface, which induced a built-in electric field for the flow of charge carriers.

Furthermore, 2D niobium phase-layered perovskite Dion-Jacobson compounds have become a hot focal field in materials science and engineering for clean energy production and environmental cleaning in the past few years (Maeda et al., 2014; Oshima et al., 2016). It is well known that the layered perovskite Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub><sup>-</sup> nanosheets, emerging from NbO<sub>6</sub> octahedra building blocks, are promising owing to their good chemical stability, high surface area, and relatively cost-effective (Sabio et al., 2010). Therefore, it is expected that by integrating the idea of Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub><sup>-</sup> nanosheets into 2D g-C<sub>3</sub>N<sub>4</sub> photocatalysts from the viewpoint of materials design, the photocatalytic efficiency of the composite nanomaterials will be exhilaratingly elevated. In a very recent work published in 2017, Chen's group designed a visible-light-responsive 2D/2D K<sup>+</sup>Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub><sup>-</sup>/g-C<sub>3</sub>N<sub>4</sub> nanosheet heterojunction, which was fabricated by a hydrothermal process (Figure 4C), for photodegradation of tetracycline hydrochloride (Jiang et al., 2017). The hybrid photocatalyst manifested a strikingly high activity, which was 6.6 and 1.8 times greater compared with that of pure K<sup>+</sup>Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub><sup>-</sup> and g-C<sub>3</sub>N<sub>4</sub>, respectively, due to the well-contacted heterointerfaces with strong interfacial coupling. Similarly, another group of researchers has synthesized the nanosheet composites by combining Ca<sub>2</sub>Nb<sub>2</sub>TaO<sub>10</sub> and g-C<sub>3</sub>N<sub>4</sub> nanosheets through a simple solution exfoliation-reassembly



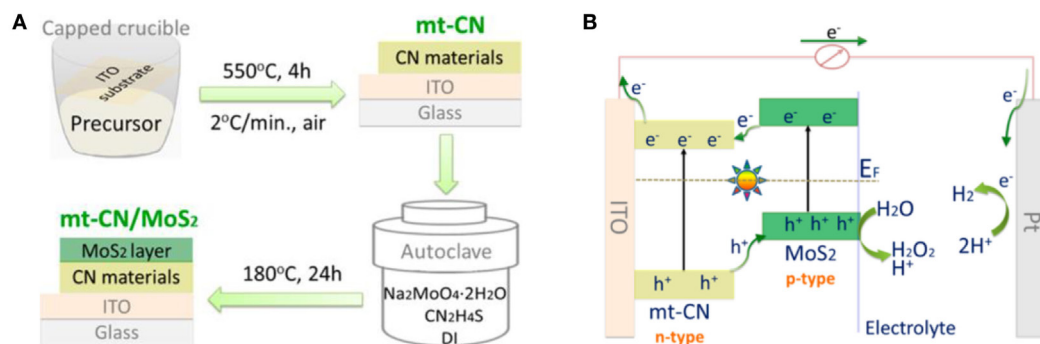

**FIGURE 3 | (A)** Synthesis route of MoS<sub>2</sub>/S-doped g-C<sub>3</sub>N<sub>4</sub> heterojunction film on ITO glass. **(B)** Charge transfer and separation of MoS<sub>2</sub>/S-doped g-C<sub>3</sub>N<sub>4</sub> photoanode via p-n heterojunctions for the improved H<sub>2</sub> generation. Reproduced from Ye et al. (2016) with permission from the American Chemical Society.

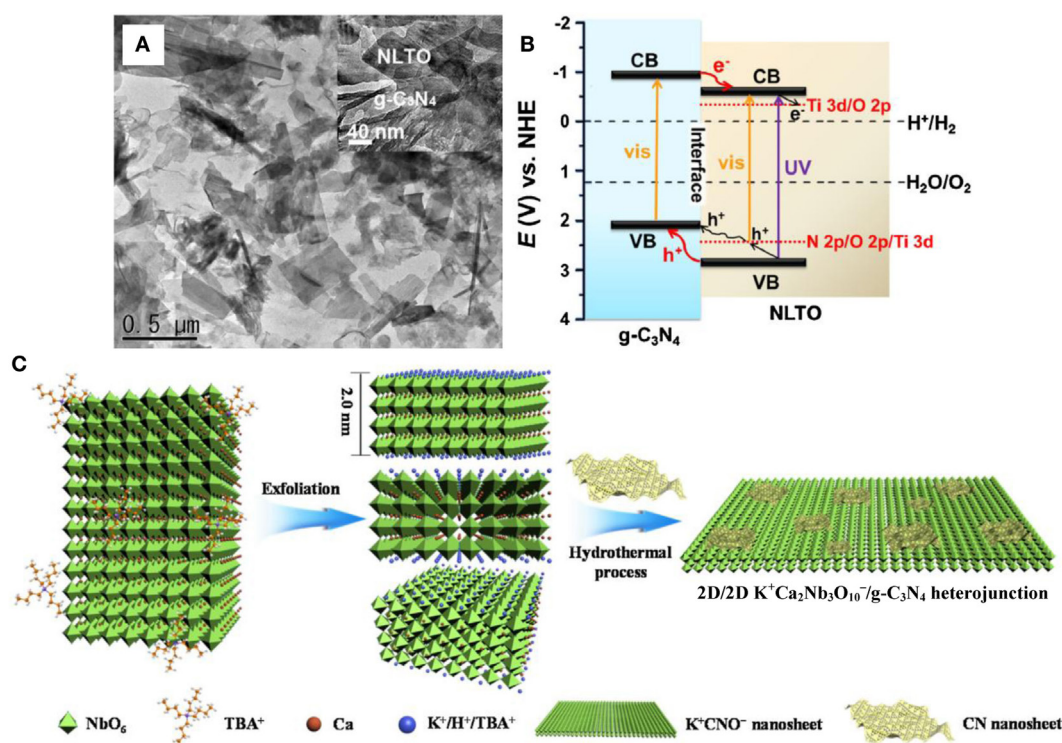

**FIGURE 4 | (A)** Transmission electron microscopy image of NLTO/g-C<sub>3</sub>N<sub>4</sub> hybrid photocatalysts. **(B)** Schematic of effective transfer of photogenerated electrons and holes across the heterojunction interface of NLTO/g-C<sub>3</sub>N<sub>4</sub> through a type II band alignment. Reproduced from Cai et al. (2017) with permission from Elsevier. **(C)** Synthesis procedure of 2D/2D K<sup>+</sup>Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub>/g-C<sub>3</sub>N<sub>4</sub>-layered nanohybrids. Reproduced from Jiang et al. (2017) with permission from Elsevier.

technique for solar H<sub>2</sub> production (Thaweesak et al., 2017). As such, it is believed that this research will cast new opportunities for engineering 2D/2D perovskite-based nanosheets coupled with g-C<sub>3</sub>N<sub>4</sub> heterojunction interface for multitudinous light-driven applications.


## Hybridization with 2D Graphene

At present,  $\pi$ -conjugated carbonaceous nanomaterials, including carbon nanotubes, grapheme, and carbon nanodots has emerged as one of the most fascinating and exciting research

directions in the past 10 years especially in the arena of environmental remediation, energy conversion, and energy storage (Tan et al., 2013; Cazorla-Amorós, 2014; Li et al., 2014; Cao and Wei, 2015; Fan, 2015; Ali Tahir et al., 2016; Carmona et al., 2016; Kotal et al., 2016; Xu et al., 2016). These carbon nanostructures have been commonly utilized as excellent reduction cocatalysts by incorporating with semiconductor photocatalysts to prolong the lifetime of charge carriers to diminish the recombination of electron-hole pairs (Xu et al., 2013; Himaja et al., 2015; Liu et al., 2015; Tan et al., 2015a; Hu, 2016; Zhang et al., 2016; Ong

et al., 2017). It is discernable that the 2D graphene has directed a worldwide trend in the materials research stemming from its large surface area, remarkable electronic, optical and mechanical features, and high chemical stability (Putri et al., 2015, 2016b; Voon et al., 2016; Xiang et al., 2016). Up to now, a plethora of literature reports has been devoted to fabricate 2D/2D graphene/g-C<sub>3</sub>N<sub>4</sub> nanohybrids for photoredox catalysis in H<sub>2</sub> evolution, pollutant degradation, and CO<sub>2</sub> reduction (Xiang et al., 2011; Li et al., 2013; Xu et al., 2015; Wan et al., 2016). In a work by Ong et al. (2015a), sandwich-like graphene/g-C<sub>3</sub>N<sub>4</sub> nanocomposites were prepared *via* a one-step impregnation-thermal reduction process by employing graphene oxide and urea as the precursors (**Figure 5A**). Interestingly, the absorption band edge of the nanohybrids was slightly red shifted toward a longer wavelength, resulting in a reduction in the band gap energy. This phenomenon was contributed by the covalent cross linker (C–O–C) formed between g-C<sub>3</sub>N<sub>4</sub> and graphene as a result of thermal heating at the high temperature. For the first time, the metal-free graphene/g-C<sub>3</sub>N<sub>4</sub> photocatalyst played a prominent role in the reduction of CO<sub>2</sub> to CH<sub>4</sub> under visible light, which was 2.3 times higher than pristine g-C<sub>3</sub>N<sub>4</sub>. In this sense, this study incontrovertibly focuses the spotlight on the innovative design of metal-free layered photocatalysts as a new class of light-active materials for a cornucopia of catalytic applications.

In another closely related work by the similar research group, the novel 2D/2D-reduced graphene oxide (rGO)-hybridized protonated g-C<sub>3</sub>N<sub>4</sub> (rGO/pCN) was rationally constructed by  $\pi$ - $\pi$  stacking and electrostatic self-assembly between the positively charged pCN and the negatively charged rGO (**Figure 5B**) (Ong et al., 2015c). In the rGO/pCN hybrid nanoarchitectures, a well-dispersed sheet-on-sheet structure of rGO and pCN confirmed the well-intact interfacial contact (**Figures 5C,D**) as compared to the rGO/g-C<sub>3</sub>N<sub>4</sub>, which employed the unmodified g-C<sub>3</sub>N<sub>4</sub> with a negatively charged surface. Essentially, the rGO/pCN heterojunction nanosheets endowed pronounced 5.4 and 1.7 times enhancement in the photoconversion of CO<sub>2</sub> to CH<sub>4</sub> with respect to the pCN and rGO/g-C<sub>3</sub>N<sub>4</sub>, respectively. Thus, this distinctly underlines the fundamental and technological importance of surface charge modification between two dissimilar 2D nanomaterials for robust interfacial interactions in unraveling the charge dynamics for enhanced photocatalysis. Benefiting from the predominant role of graphene as the electron reservoir (Zhang et al., 2012, 2015b; Tan et al., 2015b; Mateo et al., 2016; Varadwaj and Nyamori, 2016), the photoinduced electrons were transferred from pCN to rGO across the interface to overwhelmingly suppress the charge recombination rate (**Figure 5E**). All in all, the smart 2D/2D interface engineering design of graphene/g-C<sub>3</sub>N<sub>4</sub> developed thus far is considered as an auspicious means, which

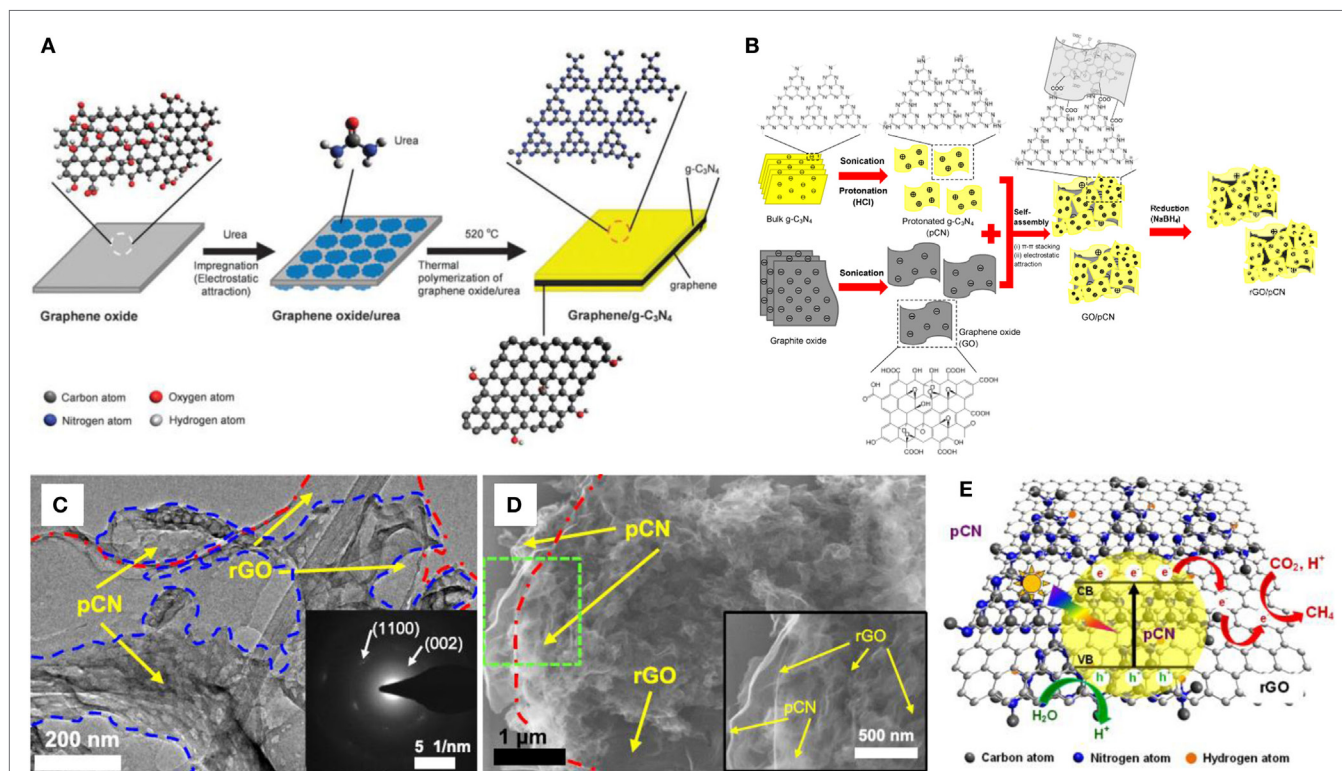

**FIGURE 5 | (A)** Fabrication of graphene/g-C<sub>3</sub>N<sub>4</sub> photocatalysts by means of a facile impregnation-thermal reduction process. Reproduced from Ong et al. (2015a) with permission from Royal Society of Chemistry. **(B)** Schematic of reduced graphene oxide (rGO)/pCN samples developed by a sonication-aided electrostatic attraction and  $\pi$ - $\pi$  interaction process. **(C)** Transmission electron microscopy and **(D)** scanning electron microscopy images of rGO/pCN samples. Inset of panel **(C)** is the selected area electron diffraction of rGO/pCN. **(E)** Reaction mechanism of photoreduction of CO<sub>2</sub> with H<sub>2</sub>O over rGO/pCN samples. Reproduced from Ong et al. (2015c) with permission from Elsevier.

could be eminently extended to heteroatom-doping graphene-hybridized g-C<sub>3</sub>N<sub>4</sub> for targeting superior photochemistry applications for real-life applications.

## CONCLUSION AND OUTLOOK

In short, the burgeoning developments of nanoscale architecturing of g-C<sub>3</sub>N<sub>4</sub>-based hybrid structures over the past 8 years have witnessed a wealth of knowledge and information for the intelligent design and myriads of applications in sustainable energy conversion and environmental purification. The applications, which encompass water splitting, H<sub>2</sub> generation, O<sub>2</sub> evolution, CO<sub>2</sub> fixation, and pollutant degradation, have readily made full use of the intriguing features of g-C<sub>3</sub>N<sub>4</sub>, namely metal-free 2D nanomaterials, earth-abundant nature of the elements, visible-light optical absorption, high redox power, and excellent chemical stability. Since the advent of g-C<sub>3</sub>N<sub>4</sub> photocatalysts by Wang et al. (2009) for H<sub>2</sub> generation, there is a rocket rise of research works on the modification of bare g-C<sub>3</sub>N<sub>4</sub> to conspicuously increase the specific surface area, introduce porosity by textural modifications, extend visible-light absorption to longer wavelengths (even up to near infra-red) for the utilization of whole solar spectrum, decrease the band gap energy and bolster the charge migration and separation.

In this mini-review, a systematic discussion on the most updated advancements of engineering 2D/2D g-C<sub>3</sub>N<sub>4</sub> heterojunction layered nanoarchitectures with boosted photoactivity has been reviewed. It is worth mentioning that albeit there is a large library of recent research discoveries on the 2D/2D g-C<sub>3</sub>N<sub>4</sub>-based photocatalysts, there exist numerous open issues, limitations, questions, and complexities of materials science, chemistry, physics, and environmental science, which require extensive research now and future. Among all, the actual mechanisms of enhanced catalytic efficiency toward the water splitting and CO<sub>2</sub> reduction followed by their respective reaction pathways are still up in the air yet until now. It is envisaged that the pertinent mechanism underlying the photocatalytic performance should be deeply explored by joining the experimental findings and theoretical computational simulations for the future research. In this manner, the rationale behind the profound photocatalytic enhancement especially on the rate determining steps of the reaction in the 2D/2D nanohybrids can be entirely comprehended. Apart from that, the charge carrier dynamics and transfer pathway for the Z-scheme system, p-n heterojunction, n-n heterojunction, Schottky junction, homojunction, and facet junction in the 2D/2D g-C<sub>3</sub>N<sub>4</sub>-based system will be facily understood. Benefiting from both experimental results and first-principles DFT calculations, this will in turn provide us a rational outline to advance the state

of the research on photocatalysis for the next breakthrough in the field of energy conversion.

Moreover, the coupling interaction between 2D g-C<sub>3</sub>N<sub>4</sub> nanosheet and another 2D semiconductor is of utmost importance for developing intact heterojunction interfaces for efficient electron-hole shuttling to prolong the lifetime of charge carriers to accelerate the photocatalytic efficiency. In-depth studies in engineering, the intimate heterointerfaces of the 2D/2D nanohybrids at a molecular level will give rise to captivating results for tuning the existing molecular structure of bare g-C<sub>3</sub>N<sub>4</sub>, thereby enhancing mobility of electron-hole pairs and subsequently improving the photocatalytic redox ability. Additionally, it is crucial to attain a facile and low-cost metal-free 2D/2D g-C<sub>3</sub>N<sub>4</sub>-based photocatalyst system without comprising metal-containing semiconductors for practical benefits. Thus, continuous efforts in exploring non-metal semiconductors to couple with g-C<sub>3</sub>N<sub>4</sub> will be advantageous for industrialization and commercialization in the long run to combat the cost concern for the large-scale processes.

To cut a long story short, it is apparent that the research progress has been tremendously impressive at this juncture by viewing at the relatively short period of time and history of g-C<sub>3</sub>N<sub>4</sub>-based photocatalysis. Undeniably, the incessant research efforts on the 2D/2D-layered nanocomposites will open new vistas and lay a strong foundation for advanced light-driven catalysis and electrocatalysis, which undeniably warrant continuous research along this direction. Without any doubts, this will act as a new paradigm for the next generation smart artificial photocatalytic systems for practical and commercial benefits in order to bridge the gap between lab-scale research and large-scale industrial applications. All in all, with the ceaseless cooperative work from all segments and disciplines in the world, the targets of building a cleaner, greener, sustainable, and zero-energy environment will be systematically accomplished in years to come. Last but not least, it is genuinely hoped that this mini-review will paint a much clearer image to direct us for the upcoming research horizons in 2D/2D photocatalysis for momentous breakthroughs in attaining highly effective, efficient, and economical g-C<sub>3</sub>N<sub>4</sub>-based system in future.

## AUTHOR CONTRIBUTIONS

W-JO carefully outlined the contents of the review and wrote the entire manuscript.

## ACKNOWLEDGMENTS

This work was financially supported by the Institute of Materials Research and Engineering (IMRE), Agency for Science, Technology and Research (A\*STAR) in Singapore.

## REFERENCES

- Ali Tahir, A., Ullah, H., Sudhagar, P., Asri Mat Teridi, M., Devadoss, A., and Sundaram, S. (2016). The application of graphene and its derivatives to energy conversion, storage, and environmental and biosensing devices. *Chem. Rec.* 16, 1591–1634. doi:10.1002/tcr.201500279
- Bai, S., Wang, L., Chen, X., Du, J., and Xiong, Y. (2015). Chemically exfoliated metallic MoS<sub>2</sub> nanosheets: a promising supporting co-catalyst for enhancing

the photocatalytic performance of TiO<sub>2</sub> nanocrystals. *Nano Res.* 8, 175–183. doi:10.1007/s12274-014-0606-9

- Bai, S., Xie, M., Kong, Q., Jiang, W., Qiao, R., Li, Z., et al. (2016). Incorporation of Pd into Pt co-catalysts toward enhanced photocatalytic water splitting. *Part. Part. Syst. Charact.* 33, 506–511. doi:10.1002/ppsc.201500239
- Bing, W., Chen, Z., Sun, H., Shi, P., Gao, N., Ren, J., et al. (2015). Visible-light-driven enhanced antibacterial and biofilm elimination activity of graphitic carbon



- nitride by embedded Ag nanoparticles. *Nano Res.* 8, 1648–1658. doi:10.1007/s12274-014-0654-1
- Cai, X., Zhang, J., Fujitsuka, M., and Majima, T. (2017). Graphitic-C<sub>3</sub>N<sub>4</sub> hybridized N-doped La<sub>2</sub>Ti<sub>2</sub>O<sub>7</sub> two-dimensional layered composites as efficient visible-light-driven photocatalyst. *Appl. Catal. B* 202, 191–198. doi:10.1016/j.apcatb.2016.09.021
- Cao, S., Low, J., Yu, J., and Jaroniec, M. (2015). Polymeric photocatalysts based on graphitic carbon nitride. *Adv. Mater.* 27, 2150–2176. doi:10.1002/adma.201500033
- Cao, Z., and Wei, B. (2015). A facile route to metal oxides/single-walled carbon nanotube macrofilm nanocomposites for energy storage. *Front. Mater.* 2:40. doi:10.3389/fmats.2015.00040
- Carmona, R. J., Velasco, L. F., Laurenti, E., Maurino, V., and Ania, C. O. (2016). Carbon materials as additives to WO<sub>3</sub> for an enhanced conversion of simulated solar light. *Front. Mater.* 3:9. doi:10.3389/fmats.2016.00009
- Cazorla-Amorós, D. (2014). Grand challenges in carbon-based materials research. *Front. Mater.* 1:6. doi:10.3389/fmats.2014.00006
- Chen, X., Shen, S., Guo, L., and Mao, S. S. (2010). Semiconductor-based photocatalytic hydrogen generation. *Chem. Rev.* 110, 6503–6570. doi:10.1021/cr1001645
- Cheng, H., Hou, J., Takeda, O., Guo, X.-M., and Zhu, H. (2015). A unique z-scheme 2D/2D nanosheet heterojunction design to harness charge transfer for photocatalysis. *J. Mater. Chem. A* 3, 11006–11013. doi:10.1039/c5ta01864a
- Dong, X., and Cheng, F. (2015). Recent development in exfoliated two-dimensional g-C<sub>3</sub>N<sub>4</sub> nanosheets for photocatalytic applications. *J. Mater. Chem. A* 3, 23642–23652. doi:10.1039/c5ta07374j
- Eftekhari, A. (2017). Molybdenum diselenide (MoSe<sub>2</sub>) for energy storage, catalysis, and optoelectronics. *Appl. Mater. Today* 8, 1–17. doi:10.1016/j.apmt.2017.01.006
- Fan, X. (2015). Graphene: a promising two-dimensional support for heterogeneous catalysts. *Front. Mater.* 1:39. doi:10.3389/fmats.2014.00039
- Fan, X., Zhang, L., Wang, M., Huang, W., Zhou, Y., Li, M., et al. (2016). Constructing carbon-nitride-based copolymers via Schiff base chemistry for visible-light photocatalytic hydrogen evolution. *Appl. Catal. B* 182, 68–73. doi:10.1016/j.apcatb.2015.09.006
- Fang, D., Xiaoying, L., Fei, Z., Xule, P., Xubiao, L., Shenglian, L., et al. (2016). Fabrication of 2D sheet-like BiOCl/carbon quantum dot hybrids via a template-free coprecipitation method and their tunable visible-light photocatalytic activities derived from different size distributions of carbon quantum dots. *Nanotechnology* 27, 065701. doi:10.1088/0957-4484/27/6/065701
- Gu, L., Wang, J., Zou, Z., and Han, X. (2014). Graphitic-C<sub>3</sub>N<sub>4</sub>-hybridized TiO<sub>2</sub> nanosheets with reactive {001} facets to enhance the UV- and visible-light photocatalytic activity. *J. Hazard. Mater.* 268, 216–223. doi:10.1016/j.jhazmat.2014.01.021
- Gui, M. M., Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2015). “CO<sub>2</sub> photocatalytic reduction: photocatalyst choice and product selectivity,” in *CO<sub>2</sub> Sequestration, Biofuels and Depollution*, eds E. Lichtfouse, J. Schwarzbauer, and D. Robert (Switzerland: Springer International Publishing), 71–104.
- Guo, L.-j., Wang, Y.-j., and He, T. (2016a). Photocatalytic reduction of CO<sub>2</sub> over heterostructure semiconductors into value-added chemicals. *Chem. Rev.* 16, 1918–1933. doi:10.1002/tcr.201600008
- Guo, Y., Song, S., Zheng, Y., Li, R., and Peng, T. (2016b). Synthesis and characterization of an A<sub>3</sub>BC type phthalocyanine and its visible-light-responsive photocatalytic H<sub>2</sub> production performance on graphitic carbon nitride. *Dalton Trans.* 45, 14071–14079. doi:10.1039/c6dt01248e
- Han, C., Wang, Y., Lei, Y., Wang, B., Wu, N., Shi, Q., et al. (2015). In situ synthesis of graphitic-C<sub>3</sub>N<sub>4</sub> nanosheet hybridized N-doped TiO<sub>2</sub> nanofibers for efficient photocatalytic H<sub>2</sub> production and degradation. *Nano Res.* 8, 1199–1209. doi:10.1007/s12274-014-0600-2
- He, Z., and Que, W. (2016). Molybdenum disulfide nanomaterials: structures, properties, synthesis and recent progress on hydrogen evolution reaction. *Appl. Mater. Today* 3, 23–56. doi:10.1016/j.apmt.2016.02.001
- Himaja, A. L., Karthik, P. S., and Singh, S. P. (2015). Carbon dots: the newest member of the carbon nanomaterials family. *Chem. Rev.* 15, 595–615. doi:10.1002/tcr.201402090
- Hou, Y., Laursen, A. B., Zhang, J., Zhang, G., Zhu, Y., Wang, X., et al. (2013a). Layered nanojunctions for hydrogen-evolution catalysis. *Angew. Chem. Int. Ed.* 52, 3621–3625. doi:10.1002/anie.201210294
- Hou, Y., Wen, Z., Cui, S., Guo, X., and Chen, J. (2013b). Constructing 2D porous graphitic C<sub>3</sub>N<sub>4</sub> nanosheets/nitrogen-doped graphene/layered MoS<sub>2</sub> ternary nanojunction with enhanced photoelectrochemical activity. *Adv. Mater.* 25, 6291–6297. doi:10.1002/adma.201303116
- Hou, Y., Wen, Z., Cui, S., Feng, X., and Chen, J. (2016). Strongly coupled ternary hybrid aerogels of N-deficient porous graphitic-C<sub>3</sub>N<sub>4</sub> nanosheets/N-doped graphene/NiFe-layered double hydroxide for solar-driven photoelectrochemical water oxidation. *Nano Lett.* 16, 2268–2277. doi:10.1021/acs.nanolett.5b04496
- Hou, Y., Zhu, Y., Xu, Y., and Wang, X. (2014). Photocatalytic hydrogen production over carbon nitride loaded with WS<sub>2</sub> as cocatalyst under visible light. *Appl. Catal. B* 15, 122–127. doi:10.1016/j.apcatb.2014.03.002
- Hu, S. (2016). Tuning optical properties and photocatalytic activities of carbon-based “quantum dots” through their surface groups. *Chem. Rev.* 16, 219–230. doi:10.1111/tcr.201500225
- Hu, S., Ma, L., Xie, Y., Li, F., Fan, Z., Wang, F., et al. (2015). Hydrothermal synthesis of oxygen functionalized S-P codoped g-C<sub>3</sub>N<sub>4</sub> nanorods with outstanding visible light activity under anoxic conditions. *Dalton Trans.* 44, 20889–20897. doi:10.1039/c5dt04035c
- Huang, Z.-F., Song, J., Pan, L., Wang, Z., Zhang, X., Zou, J.-J., et al. (2015). Carbon nitride with simultaneous porous network and O-doping for efficient solar-energy-driven hydrogen evolution. *Nano Energy* 12, 646–656. doi:10.1016/j.nanoen.2015.01.043
- Ida, S., and Ishihara, T. (2014). Recent progress in two-dimensional oxide photocatalysts for water splitting. *J. Phys. Chem. Lett.* 5, 2533–2542. doi:10.1021/jz5010957
- Inoue, T., Fujishima, A., Konishi, S., and Honda, K. (1979). Photoelectrocatalytic reduction of carbon dioxide in aqueous suspensions of semiconductor powders. *Nature* 277, 637–638. doi:10.1038/277637a0
- Jiang, D., Wang, T., Xu, Q., Li, D., Meng, S., and Chen, M. (2017). Perovskite oxide ultrathin nanosheets/g-C<sub>3</sub>N<sub>4</sub> 2D-2D heterojunction photocatalysts with significantly enhanced photocatalytic activity towards the photodegradation of tetracycline. *Appl. Catal. B* 201, 617–628. doi:10.1016/j.apcatb.2016.09.001
- Kalantar-zadeh, K., Ou, J. Z., Daeneke, T., Mitchell, A., Sasaki, T., and Fuhrer, M. S. (2016). Two dimensional and layered transition metal oxides. *Appl. Mater. Today* 5, 73–89. doi:10.1016/j.apmt.2016.09.012
- Keane, D. A., McGuigan, K. G., Ibanez, P. F., Polo-Lopez, M. I., Byrne, J. A., Dunlop, P. S. M., et al. (2014). Solar photocatalysis for water disinfection: materials and reactor design. *Catal. Sci. Technol.* 4, 1211–1226. doi:10.1039/c4cy00006d
- Kotal, M., Kim, J., Oh, J., and Oh, I.-K. (2016). Recent progress in multifunctional graphene aerogels. *Front. Mater.* 3:29. doi:10.3389/fmats.2016.00029
- Lee, H. L., Sofer, Z., Mazánek, V., Luxa, J., Chua, C. K., and Pumera, M. (2017). Graphitic carbon nitride: effects of various precursors on the structural, morphological and electrochemical sensing properties. *Appl. Mater. Today*. doi:10.1016/j.apmt.2016.09.019
- Li, C., Du, Y., Wang, D., Yin, S., Tu, W., Chen, Z., et al. (2017). Unique P-Co-N surface bonding states constructed on g-C<sub>3</sub>N<sub>4</sub> nanosheets for drastically enhanced photocatalytic activity of H<sub>2</sub> evolution. *Adv. Funct. Mater.* 27, 1604328. doi:10.1002/adfm.201604328
- Li, P., Chen, C., Zhang, J., Li, S., Sun, B., and Bao, Q. (2014). Graphene-based transparent electrodes for hybrid solar cells. *Front. Mater.* 1:26. doi:10.3389/fmats.2014.00026
- Li, X., Yu, J., and Jaroniec, M. (2016a). Hierarchical photocatalysts. *Chem. Soc. Rev.* 45, 2603–2636. doi:10.1039/c5cs00838g
- Li, Y., Wei, X., Yan, X., Cai, J., Zhou, A., Yang, M., et al. (2016b). Construction of inorganic-organic 2D/2D WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> nanosheet arrays toward efficient photoelectrochemical splitting of natural seawater. *Phys. Chem. Chem. Phys.* 18, 10255–10261. doi:10.1039/c6cp00353b
- Li, Y., Li, K., Yang, Y., Li, L., Xing, Y., Song, S., et al. (2015). Ultrathin g-C<sub>3</sub>N<sub>4</sub> nanosheets coupled with AgIO<sub>3</sub> as highly efficient heterostructured photocatalysts for enhanced visible-light photocatalytic activity. *Chem. Eur. J.* 21, 17739–17747. doi:10.1002/chem.201502945
- Li, Y., Zhang, H., Liu, P., Wang, D., Li, Y., and Zhao, H. (2013). Cross-linked g-C<sub>3</sub>N<sub>4</sub>/rGO nanocomposites with tunable band structure and enhanced visible light photocatalytic activity. *Small* 9, 3336–3344. doi:10.1002/sml.201203135
- Liang, Q., Huang, Z.-H., Kang, F., and Yang, Q.-H. (2015a). Facile synthesis of crystalline polymeric carbon nitrides with an enhanced photocatalytic performance under visible light. *ChemCatChem* 7, 2897–2902. doi:10.1002/cctc.201500076
- Liang, Q., Li, Z., Huang, Z.-H., Kang, F., and Yang, Q.-H. (2015b). Holey graphitic carbon nitride nanosheets with carbon vacancies for highly improved

- photocatalytic hydrogen production. *Adv. Funct. Mater.* 25, 6885–6892. doi:10.1002/adfm.201503221
- Liang, Q., Li, Z., Yu, X., Huang, Z.-H., Kang, F., and Yang, Q.-H. (2015c). Macroscopic 3D porous graphitic carbon nitride monolith for enhanced photocatalytic hydrogen evolution. *Adv. Mater.* 27, 4634–4639. doi:10.1002/adma.201502057
- Liang, Q., Ye, L., Xu, Q., Huang, Z.-H., Kang, F., and Yang, Q.-H. (2015d). Graphitic carbon nitride nanosheet-assisted preparation of N-enriched mesoporous carbon nanofibers with improved capacitive performance. *Carbon N. Y.* 94, 342–348. doi:10.1016/j.carbon.2015.07.001
- Linsebigler, A. L., Lu, G., and Yates, J. T. (1995). Photocatalysis on TiO<sub>2</sub> surfaces: principles, mechanisms, and selected results. *Chem. Rev.* 95, 735–758. doi:10.1021/cr00035a013
- Liu, J., Liu, Y., Liu, N., Han, Y., Zhang, X., Huang, H., et al. (2015). Metal-free efficient photocatalyst for stable visible water splitting via a two-electron pathway. *Science* 347, 970–974. doi:10.1126/science.aaa3145
- Liu, J., Wang, H., and Antonietti, M. (2016a). Graphitic carbon nitride “reloaded”: emerging applications beyond (photo)catalysis. *Chem. Soc. Rev.* 45, 2308–2326. doi:10.1039/c5cs00767d
- Liu, Q., Cao, F., Wu, F., Chen, S., Xiong, J., and Li, L. (2016b). Partial ion exchange derived 2D Cu–Zn–In–S nanosheets as sensitizers of 1D TiO<sub>2</sub> nanorods for boosting solar water splitting. *ACS Appl. Mater. Interfaces* 8, 26235–26243. doi:10.1021/acsami.6b08648
- Liu, P., Liu, Y., Ye, W., Ma, J., and Gao, D. (2016c). Flower-like N-doped MoS<sub>2</sub> for photocatalytic degradation of RhB by visible light irradiation. *Nanotechnology* 27, 225403. doi:10.1088/0957-4484/27/22/225403
- Liu, S., Zhang, N., and Xu, Y.-J. (2014). Core-shell structured nanocomposites for photocatalytic selective organic transformations. *Part. Part. Syst. Charact.* 31, 540–556. doi:10.1002/ppsc.201300235
- Liu, X., Iocozzia, J., Wang, Y., Cui, X., Chen, Y., Zhao, S., et al. (2017). Noble metal-metal oxide nanohybrids with tailored nanostructures for efficient solar energy conversion, photocatalysis and environmental remediation. *Energy Environ. Sci.* 10, 402–434. doi:10.1039/c6ee02265k
- Lu, X., Jin, Y., Zhang, X., Xu, G., Wang, D., Lv, J., et al. (2016). Controllable synthesis of graphitic C<sub>3</sub>N<sub>4</sub>/ultrathin MoS<sub>2</sub> nanosheet hybrid nanostructures with enhanced photocatalytic performance. *Dalton Trans.* 45, 15406–15414. doi:10.1039/c6dt02247b
- Ma, Y., Wang, X., Jia, Y., Chen, X., Han, H., and Li, C. (2014). Titanium dioxide-based nanomaterials for photocatalytic fuel generations. *Chem. Rev.* 114, 9987–10043. doi:10.1021/cr500008u
- Maeda, K., Eguchi, M., and Oshima, T. (2014). Perovskite oxide nanosheets with tunable band-edge potentials and high photocatalytic hydrogen-evolution activity. *Angew. Chem. Int. Ed.* 53, 13164–13168. doi:10.1002/anie.201408441
- Mamba, G., and Mishra, A. K. (2016). Graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) nanocomposites: a new and exciting generation of visible light driven photocatalysts for environmental pollution remediation. *Appl. Catal. B* 198, 347–377. doi:10.1016/j.apcatb.2016.05.052
- Mateo, D., Esteve-Adell, I., Alberio, J., Royo, J. F. S., Primo, A., and Garcia, H. (2016). 111 oriented gold nanoplatelets on multilayer graphene as visible light photocatalyst for overall water splitting. *Nat. Commun.* 7, 11819. doi:10.1038/ncomms11819
- Meng, F., Hong, Z., Arndt, J., Li, M., Zhi, M., Yang, F., et al. (2012). Visible light photocatalytic activity of nitrogen-doped La<sub>2</sub>Ti<sub>2</sub>O<sub>7</sub> nanosheets originating from band gap narrowing. *Nano Res.* 5, 213–221. doi:10.1007/s12274-012-0201-x
- Niu, P., Zhang, L., Liu, G., and Cheng, H.-M. (2012). Graphene-like carbon nitride nanosheets for improved photocatalytic activities. *Adv. Funct. Mater.* 22, 4763–4770. doi:10.1002/adfm.201200922
- Ong, W.-J., Gui, M. M., Chai, S.-P., and Mohamed, A. R. (2013). Direct growth of carbon nanotubes on Ni/TiO<sub>2</sub> as next generation catalysts for photoreduction of CO<sub>2</sub> to methane by water under visible light irradiation. *RSC Adv.* 3, 4505–4509. doi:10.1039/C3RA00030C
- Ong, W.-J., Putri, L. K., Tan, L.-L., Chai, S.-P., and Yong, S.-T. (2016a). Heterostructured AgX/g-C<sub>3</sub>N<sub>4</sub> (X = Cl and Br) nanocomposites via a sonication-assisted deposition-precipitation approach: emerging role of halide ions in the synergistic photocatalytic reduction of carbon dioxide. *Appl. Catal. B* 180, 530–543. doi:10.1016/j.apcatb.2015.06.053
- Ong, W.-J., Tan, L.-L., Ng, Y. H., Yong, S.-T., and Chai, S.-P. (2016b). Graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>)-based photocatalysts for artificial photosynthesis and environmental remediation: are we a step closer to achieving sustainability? *Chem. Rev.* 116, 7159–7329. doi:10.1021/acs.chemrev.6b00075
- Ong, W.-J., Putri, L. K., Tan, Y.-C., Tan, L.-L., Li, N., Ng, Y. H., et al. (2017). Unravelling charge carrier dynamics in protonated g-C<sub>3</sub>N<sub>4</sub> interfaced with carbon nanodots as co-catalysts toward enhanced photocatalytic CO<sub>2</sub> reduction: a combined experimental and first-principles DFT study. *Nano Res.* doi:10.1007/s12274-016-1391-4
- Ong, W.-J., Tan, L.-L., Chai, S.-P., and Yong, S.-T. (2015a). Graphene oxide as a structure-directing agent for the two-dimensional interface engineering of sandwich-like graphene-g-C<sub>3</sub>N<sub>4</sub> hybrid nanostructures with enhanced visible-light photoreduction of CO<sub>2</sub> to methane. *Chem. Commun.* 51, 858–861. doi:10.1039/c4cc08996k
- Ong, W.-J., Tan, L.-L., Chai, S.-P., and Yong, S.-T. (2015b). Heterojunction engineering of graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) via Pt loading with improved daylight-induced photocatalytic reduction of carbon dioxide to methane. *Dalton Trans.* 44, 1249–1257. doi:10.1039/c4dt02940b
- Ong, W.-J., Tan, L.-L., Chai, S.-P., Yong, S.-T., and Mohamed, A. R. (2015c). Surface charge modification via protonation of graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) for electrostatic self-assembly construction of 2D/2D reduced graphene oxide (rGO)/g-C<sub>3</sub>N<sub>4</sub> nanostructures toward enhanced photocatalytic reduction of carbon dioxide to methane. *Nano Energy* 13, 757–770. doi:10.1016/j.nanoen.2015.03.014
- Ong, W.-J., Tan, L.-L., Chai, S.-P., Yong, S.-T., and Mohamed, A. R. (2014a). Facet-dependent photocatalytic properties of TiO<sub>2</sub>-based composites for energy conversion and environmental remediation. *ChemSusChem* 7, 690–719. doi:10.1002/cssc.201300924
- Ong, W.-J., Tan, L.-L., Chai, S.-P., Yong, S.-T., and Mohamed, A. R. (2014b). Highly reactive {001} facets of TiO<sub>2</sub>-based composites: synthesis, formation mechanism and characterizations. *Nanoscale* 6, 1946–2008. doi:10.1039/c3nr04655a
- Ong, W.-J., Tan, L.-L., Chai, S.-P., Yong, S.-T., and Mohamed, A. R. (2014c). Self-assembly of nitrogen-doped TiO<sub>2</sub> with exposed {001} facets on a graphene scaffold as photo-active hybrid nanostructures for reduction of carbon dioxide to methane. *Nano Res.* 7, 1528–1547. doi:10.1007/s12274-014-0514-z
- Ong, W.-J., Voon, S.-Y., Tan, L.-L., Goh, B. T., Yong, S.-T., and Chai, S.-P. (2014d). Enhanced daylight-induced photocatalytic activity of solvent exfoliated graphene (SEG)/ZnO hybrid nanocomposites towards degradation of reactive black 5. *Ind. Eng. Chem. Res.* 53, 17333–17344. doi:10.1021/ie5027088
- Ong, W.-J., Yeong, J.-J., Tan, L.-L., Goh, B. T., Yong, S.-T., and Chai, S.-P. (2014e). Synergistic effect of graphene as a co-catalyst for enhanced daylight-induced photocatalytic activity of Zn<sub>0.5</sub>Cd<sub>0.5</sub>S synthesized via an improved one-pot co-precipitation-hydrothermal strategy. *RSC Adv.* 4, 59676–59685. doi:10.1039/c4ra10467f
- Oshima, T., Eguchi, M., and Maeda, K. (2016). Photocatalytic water oxidation over metal oxide nanosheets having a three-layer perovskite structure. *ChemSusChem* 9, 396–402. doi:10.1002/cssc.201501237
- Osterloh, F. E. (2017). Photocatalysis versus photosynthesis – a sensitivity analysis of devices for solar energy conversion and chemical transformations. *ACS Energy Lett.* 2, 445–453. doi:10.1021/acsenenergylett.6b00665
- Pan, Z., Zheng, Y., Guo, F., Niu, P., and Wang, X. (2017). Decorating CoP and Pt nanoparticles on graphitic carbon nitride nanosheets to promote overall water splitting by conjugated polymers. *ChemSusChem* 10, 87–90. doi:10.1002/cssc.201600850
- Putri, L. K., Ng, B.-J., Ong, W.-J., Lee, H. W., Chang, W. S., and Chai, S.-P. (2017). Heteroatom nitrogen- and boron-doping as a facile strategy to improve photocatalytic activity of standalone reduced graphene oxide in hydrogen evolution. *ACS Appl. Mater. Interfaces* 9, 4558–4569. doi:10.1021/acsami.6b12060
- Putri, L. K., Ong, W.-J., Chang, W. S., and Chai, S.-P. (2015). Heteroatom doped graphene in photocatalysis: a review. *Appl. Surf. Sci.* 358(Part A), 2–14. doi:10.1016/j.apsusc.2015.08.177
- Putri, L. K., Ong, W.-J., Chang, W. S., and Chai, S.-P. (2016a). Enhancement in the photocatalytic activity of carbon nitride through hybridization with light-sensitive AgCl for carbon dioxide reduction to methane. *Catal. Sci. Technol.* 6, 744–754. doi:10.1039/c5cy00767d
- Putri, L. K., Tan, L.-L., Ong, W.-J., Chang, W. S., and Chai, S.-P. (2016b). Graphene oxide: exploiting its unique properties toward visible-light-driven photocatalysis. *Appl. Mater. Today* 4, 9–16. doi:10.1016/j.apmt.2016.04.001
- Rahman, M. Z., Ran, R. J., Tang, Y., Jaroniec, M., and Qiao, S. (2016). Surface activated carbon nitride nanosheets with optimized electro-optical properties



- for highly efficient photocatalytic hydrogen production. *J. Mater. Chem. A* 4, 2445–2452. doi:10.1039/c5ta10194h
- Roger, I., Shipman, M. A., and Symes, M. D. (2017). Earth-abundant catalysts for electrochemical and photoelectrochemical water splitting. *Nat. Rev. Chem.* 1, 0003. doi:10.1038/s41570-016-0003
- Sabio, E. M., Chi, M., Browning, N. D., and Osterloh, F. E. (2010). Charge separation in a niobate nanosheet photocatalyst studied with photochemical labeling. *Langmuir* 26, 7254–7261. doi:10.1021/la904377f
- She, X., Wu, J., Xu, H., Mo, Z., Lian, J., Song, Y., et al. (2017). Enhancing charge density and steering charge unidirectional flow in 2D non-metallic semiconductor-CNTs-metal coupled photocatalyst for solar energy conversion. *Appl. Catal. B* 202, 112–117. doi:10.1016/j.apcatb.2016.09.013
- She, X., Wu, J., Zhong, J., Xu, H., Yang, Y., Vajtai, R., et al. (2016). Oxygenated monolayer carbon nitride for excellent photocatalytic hydrogen evolution and external quantum efficiency. *Nano Energy* 27, 138–146. doi:10.1016/j.nanoen.2016.06.042
- Shi, L., Chang, K., Zhang, H., Hai, X., Yang, L., Wang, T., et al. (2016). Drastic enhancement of photocatalytic activities over phosphoric acid protonated porous g-C<sub>3</sub>N<sub>4</sub> nanosheets under visible light. *Small* 12, 4431–4439. doi:10.1002/smll.201601668
- Tan, L.-L., Ong, W.-J., Chai, S.-P., Goh, B. T., and Mohamed, A. R. (2015a). Visible-light-active oxygen-rich TiO<sub>2</sub> decorated 2D graphene oxide with enhanced photocatalytic activity towards carbon dioxide reduction. *Appl. Catal. B* 179, 160–170. doi:10.1016/j.apcatb.2015.05.024
- Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2015b). Noble metal modified reduced graphene oxide/TiO<sub>2</sub> ternary nanostructures for efficient visible-light-driven photoreduction of carbon dioxide into methane. *Appl. Catal. B* 16, 251–259. doi:10.1016/j.apcatb.2014.11.035
- Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2013). Growth of carbon nanotubes over non-metallic based catalysts: a review on the recent developments. *Catal. Today* 217, 1–12. doi:10.1016/j.cattod.2012.10.023
- Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2014). Band gap engineered, oxygen-rich TiO<sub>2</sub> for visible light induced photocatalytic reduction of CO<sub>2</sub>. *Chem. Commun.* 50, 6923–6926. doi:10.1039/c4cc01304b
- Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2016). Visible-light-activated oxygen-rich TiO<sub>2</sub> as next generation photocatalyst: importance of annealing temperature on the photoactivity toward reduction of carbon dioxide. *Chem. Eng. J.* 283, 1254–1263. doi:10.1016/j.cej.2015.07.093
- Tan, L.-L., Ong, W.-J., Chai, S.-P., and Mohamed, A. R. (2017). Photocatalytic reduction of CO<sub>2</sub> with H<sub>2</sub>O over graphene oxide-supported oxygen-rich TiO<sub>2</sub> hybrid photocatalyst under visible light irradiation: process and kinetic studies. *Chem. Eng. J.* 308, 248–255. doi:10.1016/j.cej.2016.09.050
- Thaweesak, S., Lyu, M., Peerakiatkhajohn, P., Butburee, T., Luo, B., Chen, H., et al. (2017). Two-dimensional g-C<sub>3</sub>N<sub>4</sub>/Ca<sub>2</sub>Nb<sub>2</sub>TaO<sub>10</sub> nanosheet composites for efficient visible light photocatalytic hydrogen evolution. *Appl. Catal. B* 202, 184–190. doi:10.1016/j.apcatb.2016.09.022
- Tonda, S., Kumar, S., Kandula, S., and Shanker, V. (2014). Fe-doped and -mediated graphitic carbon nitride nanosheets for photocatalytic performance under natural sunlight. *J. Mater. Chem. A* 2, 6772–6780. doi:10.1039/c3ta15358d
- Tong, Z., Yang, D., Li, Z., Nan, Y., Ding, F., Shen, Y., et al. (2017). Thylakoid-inspired multishell g-C<sub>3</sub>N<sub>4</sub> nanocapsules with enhanced visible-light harvesting and electron transfer properties for high-efficiency photocatalysis. *ACS Nano* 11, 1103–1112. doi:10.1021/acsnano.6b08251
- Topcu, S., Jodhani, G., and Gouma, P. (2016). Optimized nanostructured TiO<sub>2</sub> photocatalysts. *Front. Mater.* 3:35. doi:10.3389/fmats.2016.00035
- Varadwaj, G. B. B., and Nyamori, V. O. (2016). Layered double hydroxide- and graphene-based hierarchical nanocomposites: synthetic strategies and promising applications in energy conversion and conservation. *Nano Res.* 9, 3598–3621. doi:10.1007/s12274-016-1250-3
- Voon, S.-Y., Ong, W.-J., Tan, L.-L., Yong, S.-T., and Chai, S.-P. (2016). “Graphene-based semiconductor materials for photocatalytic applications” in *Graphene Science Handbook: Size-Dependent Properties*, eds M. Aliofkhazraei, N. Ali, W. I. Milne, C. S. Ozkan, S. Mitura, and J. L. Gervasoni (Florida, USA: CRC Press), 331–352.
- Wan, W., Yu, S., Dong, F., Zhang, Q., and Zhou, Y. (2016). Efficient C<sub>3</sub>N<sub>4</sub>/graphene oxide macroscopic aerogel visible-light photocatalyst. *J. Mater. Chem. A* 4, 7823–7829. doi:10.1039/c6ta01804a
- Wang, J., Guan, Z., Huang, J., Li, Q., and Yang, J. (2014). Enhanced photocatalytic mechanism for the hybrid g-C<sub>3</sub>N<sub>4</sub>/MoS<sub>2</sub> nanocomposite. *J. Mater. Chem. A* 2, 7960–7966. doi:10.1039/c4ta00275j
- Wang, X., Maeda, K., Thomas, A., Takanabe, K., Xin, G., Carlsson, J. M., et al. (2009). A metal-free polymeric photocatalyst for hydrogen production from water under visible light. *Nat. Mater.* 8, 76–80. doi:10.1038/nmat2317
- Wei, Y., Su, J., Wan, X., Guo, L., and Vayssieres, L. (2016). Spontaneous photoelectric field-enhancement effect prompts the low cost hierarchical growth of highly ordered heteronanostructures for solar water splitting. *Nano Res.* 9, 1561–1569. doi:10.1007/s12274-016-1050-9
- Wen, J., Xie, J., Shen, R., Li, X., Luo, X., Zhang, H., et al. (2017). Markedly enhanced visible-light photocatalytic H<sub>2</sub> generation over g-C<sub>3</sub>N<sub>4</sub> nanosheets decorated by robust nickel phosphide (Ni<sub>12</sub>P<sub>3</sub>) cocatalysts. *Dalton Trans.* 46, 1794–1802. doi:10.1039/c6dt04575h
- Wenderich, K., and Mul, G. (2016). Methods, mechanism, and applications of photodeposition in photocatalysis: a review. *Chem. Rev.* 116, 14587–14619. doi:10.1021/acs.chemrev.6b00327
- Xia, P., Zhu, B., Yu, J., Cao, S., and Jaroniec, M. (2017). Ultra-thin nanosheet assemblies of graphitic carbon nitride for enhanced photocatalytic CO<sub>2</sub> reduction. *J. Mater. Chem. A* 5, 3230–3238. doi:10.1039/c6ta08310b
- Xiang, Q., Cheng, F., and Lang, D. (2016). Hierarchical layered WS<sub>2</sub>/graphene-modified CdS nanorods for efficient photocatalytic hydrogen evolution. *ChemSusChem* 9, 996–1002. doi:10.1002/cssc.201501702
- Xiang, Q., Yu, J., and Jaroniec, M. (2011). Preparation and enhanced visible-light photocatalytic H<sub>2</sub>-production activity of graphene/C<sub>3</sub>N<sub>4</sub> composites. *J. Phys. Chem. C* 115, 7355–7363. doi:10.1021/jp200953k
- Xing, W., Li, C., Wang, Y., Han, Z., Hu, Y., Chen, D., et al. (2017). A novel 2D/2D carbonized poly-(furfural alcohol)/g-C<sub>3</sub>N<sub>4</sub> nanocomposites with enhanced charge carrier separation for photocatalytic H<sub>2</sub> evolution. *Carbon N. Y.* 115, 486–492. doi:10.1016/j.carbon.2017.01.045
- Xu, J., Gu, P., Zhang, J., Xue, H., and Pang, H. (2016). Copper-based nanomaterials for high-performance lithium-ion batteries. *Part. Part. Syst. Charact.* 33, 784–810. doi:10.1002/ppsc.201600150
- Xu, L., Huang, W.-Q., Wang, L.-L., Tian, Z.-A., Hu, W., Ma, Y., et al. (2015). Insights into enhanced visible-light photocatalytic hydrogen evolution of g-C<sub>3</sub>N<sub>4</sub> and highly reduced graphene oxide composite: the role of oxygen. *Chem. Mater.* 27, 1612–1621. doi:10.1021/cm504265w
- Xu, Y., Xu, H., Wang, L., Yan, J., Li, H., Song, Y., et al. (2013). The CNT modified white C<sub>3</sub>N<sub>4</sub> composite photocatalyst with enhanced visible-light response photoactivity. *Dalton Trans.* 42, 7604–7613. doi:10.1039/c3dt32871f
- Xueting, C., Xinxin, Z., Shibin, S., Danxia, G., Lihua, D., Yansheng, Y., et al. (2017). MnO<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> nanocomposite with highly enhanced supercapacitor performance. *Nanotechnology* 28, 135705. doi:10.1088/1361-6528/aa6107
- Ye, L., Wang, D., and Chen, S. (2016). Fabrication and enhanced photoelectrochemical performance of MoS<sub>2</sub>/S-doped g-C<sub>3</sub>N<sub>4</sub> heterojunction film. *ACS Appl. Mater. Interfaces* 8, 5280–5289. doi:10.1021/acsaami.5b11326
- Ye, M.-Y., Zhao, Z.-H., Hu, Z.-F., Liu, L.-Q., Ji, H.-M., Shen, Z.-R., et al. (2017). 0D/2D heterojunctions of vanadate quantum dots/graphitic carbon nitride nanosheets for enhanced visible-light-driven photocatalysis. *Angew. Chem. Int. Ed.* doi:10.1002/anie.201611127
- Yi, S.-S., Yan, J.-M., Wulan, B.-R., Li, S.-J., Liu, K.-H., and Jiang, Q. (2017). Noble-metal-free cobalt phosphide modified carbon nitride: an efficient photocatalyst for hydrogen generation. *Appl. Catal. B* 200, 477–483. doi:10.1016/j.apcatb.2016.07.046
- Yin, S., Han, J., Zhou, T., and Xu, R. (2015). Recent progress in g-C<sub>3</sub>N<sub>4</sub> based low cost photocatalytic system: activity enhancement and emerging applications. *Catal. Sci. Technol.* 5, 5048–5061. doi:10.1039/c5cy00938c
- Yu, X., and Sivula, K. (2016). Toward large-area solar energy conversion with semi-conducting 2D transition metal dichalcogenides. *ACS Energy Lett.* 1, 315–322. doi:10.1021/acsenenergylett.6b00114
- Yubin, C., Chi-Hung, C., Zhixiao, Q., Shaohua, S., Tennyson, D., and Clemens, B. (2017). Electron-transfer dependent photocatalytic hydrogen generation over cross-linked CdSe/TiO<sub>2</sub> type-II heterostructure. *Nanotechnology* 28, 084002. doi:10.1088/1361-6528/aa5642
- Zhang, H., Liu, G., Shi, L., Liu, H., Wang, T., and Ye, J. (2016a). Engineering coordination polymers for photocatalysis. *Nano Energy* 22, 149–168. doi:10.1016/j.nanoen.2016.01.029

- Zhang, Q., Hu, S., Fan, Z., Liu, D., Zhao, Y., Ma, H., et al. (2016b). Preparation of g-C<sub>3</sub>N<sub>4</sub>/ZnMoCdS hybrid heterojunction catalyst with outstanding nitrogen photofixation performance under visible light via hydrothermal post-treatment. *Dalton Trans.* 45, 3497–3505. doi:10.1039/c5dt04901f
- Zhang, Y., Zhou, Y., Tang, L., Wang, M., Li, P., Tu, W., et al. (2016c). Fabrication of oxygen-doped double-shelled GaN hollow spheres toward efficient photoreduction of CO<sub>2</sub>. *Part. Part. Syst. Charact.* 33, 583–588. doi:10.1002/ppsc.201500235
- Zhang, Z., Jiang, D., Li, D., He, M., and Chen, M. (2016d). Construction of SnNb<sub>2</sub>O<sub>6</sub> nanosheet/g-C<sub>3</sub>N<sub>4</sub> nanosheet two-dimensional heterostructures with improved photocatalytic activity: synergistic effect and mechanism insight. *Appl. Catal. B* 183, 113–123. doi:10.1016/j.apcatb.2015.10.022
- Zhang, Z., Liu, K., Feng, Z., Bao, Y., and Dong, B. (2016e). Hierarchical sheet-on-sheet ZnIn<sub>2</sub>S<sub>4</sub>/g-C<sub>3</sub>N<sub>4</sub> heterostructure with highly efficient photocatalytic H<sub>2</sub> production based on photoinduced interfacial charge transfer. *Sci. Rep.* 6, 19221. doi:10.1038/srep19221
- Zhang, Z., Zheng, T., Li, X., Xu, J., and Zeng, H. (2016f). Progress of carbon quantum dots in photocatalysis applications. *Part. Part. Syst. Charact.* 33, 457–472. doi:10.1002/ppsc.201500243
- Zhang, C., Lu, Y., Jiang, Q., and Hu, J. (2016g). Synthesis of CdS hollow spheres coupled with g-C<sub>3</sub>N<sub>4</sub> as efficient visible-light-driven photocatalysts. *Nanotechnology* 27, 355402. doi:10.1088/0957-4484/27/35/355402
- Zhang, J., Chen, Y., and Wang, X. (2015a). Two-dimensional covalent carbon nitride nanosheets: synthesis, functionalization, and applications. *Energy Environ. Sci.* 8, 3092–3108. doi:10.1039/c5ee01895a
- Zhang, N., Yang, M.-Q., Liu, S., Sun, Y., and Xu, Y.-J. (2015b). Waltzing with the versatile platform of graphene to synthesize composite photocatalysts. *Chem. Rev.* 115, 10307–10377. doi:10.1021/acs.chemrev.5b00267
- Zhang, N., Zhang, Y., and Xu, Y.-J. (2012). Recent progress on graphene-based photocatalysts: current status and future perspectives. *Nanoscale* 4, 5792–5813. doi:10.1039/c2nr31480k
- Zhao, H., Jiang, P., and Cai, W. (2017a). Graphitic C<sub>3</sub>N<sub>4</sub> decorated with CoP co-catalyst: enhanced and stable photocatalytic H<sub>2</sub> evolution activity from water under visible-light irradiation. *Chem. Asian J.* 12, 361–365. doi:10.1002/asia.201601543
- Zhao, H., Sun, S., Jiang, P., and Xu, Z. J. (2017b). Graphitic C<sub>3</sub>N<sub>4</sub> modified by Ni<sub>2</sub>P cocatalyst: an efficient, robust and low cost photocatalyst for visible-light-driven H<sub>2</sub> evolution from water. *Chem. Eng. J.* 315, 296–303. doi:10.1016/j.cej.2017.01.034
- Zhao, J., Ke, X., Liu, H., Huang, Y., Chen, C., Bo, A., et al. (2016a). Comparing the contribution of visible-light irradiation, gold nanoparticles, and titania supports in photocatalytic nitroaromatic coupling and aromatic alcohol oxidation. *Part. Part. Syst. Charact.* 33, 628–634. doi:10.1002/ppsc.201600049
- Zhao, L., Xu, H., Jiang, B., and Huang, Y. (2016b). Synergetic photocatalytic nanostructures based on Au/TiO<sub>2</sub>/reduced graphene oxide for efficient degradation of organic pollutants. *Part. Part. Syst. Charact.* doi:10.1002/ppsc.201600323
- Zhao, Z., Sun, Y., and Dong, F. (2015). Graphitic carbon nitride based nanocomposites: a review. *Nanoscale* 7, 15–37. doi:10.1039/c4nr03008g
- Zheng, D., Huang, C., and Wang, X. (2015). Post-annealing reinforced hollow carbon nitride nanospheres for hydrogen photosynthesis. *Nanoscale* 7, 465–470. doi:10.1039/c4nr06011c
- Zhou, H., Li, P., Liu, J., Chen, Z., Liu, L., Dontsova, D., et al. (2016). Biomimetic polymeric semiconductor based hybrid nanosystems for artificial photosynthesis towards solar fuels generation via CO<sub>2</sub> reduction. *Nano Energy* 25, 128–135. doi:10.1016/j.nanoen.2016.04.049

**Conflict of Interest Statement:** The author declares that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Copyright © 2017 Ong. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) or licensor are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.